



## Research Article

# Cefuroxime Axetil: A Commercially Available Pro-Drug as Corrosion Inhibitor for Aluminum in Hydrochloric Acid Solution

Paul O Ameh\* and Umar M. Sani

### Abstract

Cefuroxime axetil (CA) a pro-drug was tested as corrosion inhibitor for aluminum in hydrochloric acid solution using thermometric, gasometric weight loss and scanning electron microscope (SEM) techniques. Results obtained showed that this compound has good inhibiting properties for aluminum corrosion in acidic medium, with inhibition efficiencies values reaching 89.87 % at 0.5 g / L. It was also found out that the results from weight loss method are highly consistent with those obtained by hydrogen evolution method and gasometric method; and all indicate that inhibitor efficiency increases with increasing inhibitor concentration. Cefuroxime axetil inhibited the corrosion of aluminum in solutions of HCl through the mechanism of physisorption as confirmed by values of activation energy and free energy of adsorption. The adsorption of the inhibitor was also found to be spontaneous, exothermic and best fitted the Langmuir adsorption model. SEM analysis confirmed the existence of an adsorbed protective film on the aluminum surface.

**Keywords:** Adsorption; Aluminium; Corrosion Inhibition; Cefuroxime axetil, SEM

### Introduction

In developed and developing countries, billions of dollars every year are spent on capital replacement and control methods for corrosion infrastructure [1,2]. In recent years, owing to the growing interest and attention of the world towards the protection of the environment and the hazardous effects of using chemicals on the ecological balance, the use of eco-friendly inhibitors to replace the older, which is more toxic and harmful to the environment are being intensified [3-5].

Research has shown that for an inhibitor to be an effective protector against metal corrosion, it should be readily adsorbed on the metal surface through either physisorption or chemisorption processes [6-11]. Either of these adsorption processes depends primarily on the physicochemical properties of the inhibitor group such as functional groups, electronic density at the donor atom, molecular structure, etc. For instance, organic molecules, which have had a wide applicability and that have been extensively studied and used as corrosion inhibitors, often contain the heteroatoms nitrogen, oxygen, and sulfur atoms, as well as multiple bonds in their molecules. Several researches have been carried out on the use of drugs as corrosion inhibitors for several metals in various media. For example, Fouda *et al.*, studied the corrosion inhibition characteristics of floxacillin, cloxacillin, dicloxacillin, cefadroxil and cephalixin on aluminum in 0.5 M H<sub>3</sub>PO<sub>4</sub> using weight loss and galvanostatic polarization techniques [12]. Results obtained revealed that the inhibition occurs through adsorption of the inhibitor molecules on the metal surface.

Other drugs that have been found to be good corrosion inhibitors include norfloxacin, Streptomycin, Cefatrexyl, and Cefazolin [13-15]. The choice of some of the drugs used as corrosion inhibitors may be due to the fact that they have a large number of functional adsorption centers, are biodegradable, can be easily produced and purified.

In the present investigation, the corrosion inhibiting behavior of Cefuroxime axetil [Chemical name: 1-Acetoxyethyl (6R,7R)-3-[(aminocarbonyl)oxy]methyl}-7-[[2Z)-2-(2-furyl)-2-(methoxyimino) acetyl]amino}-8-oxo-5-thia-1-azabicyclo[4.2.0]oct-2-ene-



### Affiliation:

Department of Chemistry, Nigeria Police Academy Wudil, Kano State, Nigeria

### \*Corresponding author:

Paul O Ameh, Department of Chemistry, Nigeria Police Academy Wudil, Kano State, Nigeria  
E-mail: nocaseoche@yahoo.com

**Citation:** Ameh OP, Sani UM (2015) Cefuroxime Axetil: A Commercially Available Pro-Drug as Corrosion Inhibitor for Aluminum in Hydrochloric Acid Solution. J O Heterocyclics 101: 1-6

**Received:** August 12, 2015

**Accepted:** September 19, 2015

**Published:** September 26, 2015

**Copyright:** © 2015 Ameh OP, et al. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.



2-carboxylate] was investigated on aluminum in hydrochloric acid at 303 and 333 K using weight loss, thermometric gasometric and scanning electron microscope techniques.

Cefuroxime is a broad-spectrum,  $\beta$ -lactamase-stable second generation cephalosporin antibiotic drug with well-defined pharmacokinetics after injection [16]. It is commercially available for parenteral (intramuscular and intravenous) administration as a sodium salt and for oral administration as cefuroxime axetil, the 1-(acetoxylethyl ester of the drug [17]. In humans, gastrointestinal absorption of cefuroxime is negligible, whereas cefuroxime axetil shows a bioavailability of 30 to 40% when taken on fasting and 50 to 60% when taken after food [18-23]. In fact like the other cephalosporins, the parenteral cefuroxime, is not orally absorbed due to the presence of a highly polar carboxyl group that is ionized at intestinal pH, making transport across intestinal mucosa unlikely [24,25]. Cefuroxime axetil is a prodrug of cefuroxime and has little, if any, antibacterial activity until hydrolyzed in vivo to cefuroxime. The cefuroxime axetil esterase can hydrolyze cefuroxime axetil to the non-absorbable cefuroxime in the gut lumen [26]. Esterase hydrolysis leads to ethanoic acid and an unstable hydroxyethyl ester, which dissociates rapidly to ethanol and the parent cefuroxime [27]. Figure 1 shows the chemical structures of both cefuroxime and cefuroxime axetil.

The selection of cefuroxime axetil as a corrosion inhibitor is based on the following facts:

1. It contains three kinds of heteroatoms (four nitrogen, ten oxygen and one sulphur atom) as reactive center through which they can adsorb readily on the metal surface.
2. The compound is readily soluble in medium.
3. It does not cause any health hazards, but also find its diverse applications in various biological and pharmacological activities; hence the use of Cefuroxime axetil as corrosion inhibitors is safe.

## Materials and Methods

### Weight loss method

A previously weighed metal (aluminum sheet) was completely immersed in 250 ml of the test solution in an open beaker. The beaker was inserted into a water bath maintained at a temperature of 30 °C. Similar experiments were repeated at 60°C. In each case, the weight of the sample before immersion was measured using Scaltec high precision balance (Model SPB31) After every 24

hours, each sample was removed from the test solution, washed in a solution of NaOH containing zinc dust and dried in acetone before re-weighing. The difference in weight for a period of 168 hours was taken as total weight loss. The inhibition efficiency (% I) for each inhibitor was calculated using equation (1) [28]

$$\%I = \left(1 - \frac{W_1}{W_2}\right) \times 100 \quad (1)$$

Where,  $W_1$  and  $W_2$  are the weight losses ( $\text{g}/\text{dm}^3$ ) for mild steel in the presence and absence of inhibitor in HCl solution respectively. The degree of surface coverage  $\theta$  is given by the equation (2) [29]:

$$\theta = \left(1 - \frac{W_1}{W_2}\right) \quad (2)$$

The corrosion rates for mild steel corrosion in different concentrations of the acid was determined for 168 h immersion period from weight loss using equation (3) [6]

$$\text{Corrosion rate (mpy)} = \frac{534W}{DAT} \quad (3)$$

Where,  $W$  = weight loss (mg);  $D$  = density of specimen ( $\text{g}/\text{cm}^3$ ),  $A$  = area of specimen (square inches) and  $T$  = period of immersion (hour).

### Gasometry method

The method used for hydrogen evolution measurement is as described elsewhere [30]. The test solution (different concentrations of acid, inhibitor or their mixtures) was poured into the reaction vessel (gasometer). Upon the introduction of mild steel, the flask was quickly corked and the rise in volume of the paraffin due to hydrogen evolution was noted after every minute until a steady volume was observed. From the results obtained, the corrosion inhibition efficiency was calculated using the following equation,

$$\%IE = \frac{V_b - V_t}{V_b} \times 100 \quad (4)$$

Where,  $V_b$  is the volume of hydrogen gas evolved by the blank and  $V_t$  is the volume of hydrogen gas evolved in the presence of the inhibitor, after time,  $t$ .

### Thermometric method

This was also carried out as reported elsewhere [31]. The reaction number (RN) of each system was calculated by dividing the difference between the highest and lowest temperature attained by the time interval. From the reaction number, the inhibition efficiency (% I) of the inhibitor was calculated using equation (5)

$$\%I = \frac{RN_{aq} - RN_{wi}}{RN_{aq}} \times 100 \quad (5)$$

Where,  $RN_{aq}$  is the reaction number in the absence of inhibitors (blank solution) and  $RN_{wi}$  is the reaction number of 2 M HCl containing the studied inhibitor.

### Scanning electron microscopy

The scanning electron microscope (SEM) Model No JSM-5600 LV was used to study the morphology of corroded in the presence and absence of inhibitor. The photographs were taken

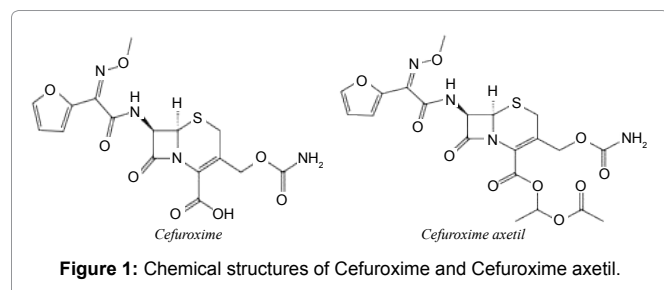


Figure 1: Chemical structures of Cefuroxime and Cefuroxime axetil.



from that portion of the specimen where better information was expected.

## Results and Discussions

### Effect of cefuroxime axetil

The corrosion rate (CR) and reaction number (RN) of aluminum in HCl containing various concentrations of Cefuroxime axetil determined for 168h immersion period from gravimetric, gasometric and thermometric are presented in Table 1. The results obtained indicates that the aluminum corrosion is reduced by the presence of Cefuroxime axetil in HCL at all concentrations used in this study, since there is a general decrease in the rate of corrosion of the aluminum with increase in concentration of the inhibitor. This may be ascribed to the adsorption of this compound on the aluminum, producing a barrier, which isolates the surface from the corrosion environment.

Table 2. presents inhibition efficiencies of various concentrations of Cefuroxime axetil in HCL. The inhibition efficiency was estimated to be 73.40 % even at extremely low inhibition concentration (0.1 M) and reaches 89.87 % at a concentration of 0.5 M. Such remarkable performances may be due to, the high molecular weight of CA, the presence of C=N, O-H, C=O, etc. which are electron donation groups and the presence of aryl groups. The inhibition efficiency was found to increase with increase in the concentration of the inhibitor but decreases with increase in temperature indicating that the mechanism of physical adsorption favours the adsorption of Cefuroxime axetil on aluminum surface. For a physical adsorption mechanism, the inhibition efficiency is expected to decrease with increase in temperature but for a chemical adsorption mechanism, the reverse is expected [31].

Also, the inhibition efficiency of CA obtained from the two methods were found correlate strongly ( $R^2 = 0.8798$  and  $0.9644$  for gasometric and thermometric respectively) with those obtained

C (g/l)	Gravimetric		Gasometric		Thermometric
	CR x 10 <sup>-5</sup> (gcm <sup>-3</sup> h <sup>-1</sup> ) at 303 K	CR x 10 <sup>-5</sup> (gcm <sup>-3</sup> h <sup>-1</sup> ) at 333 K	CR (cm <sup>3</sup> /min) at 303K	CR(cm <sup>3</sup> /min) at 333K	RN at 303K
0.1	22.56	46.5	0.0514	1.6252	0.0715
0.2	9.84	27.11	0.0463	1.0371	0.0522
0.3	6.45	15.84	0.0385	0.6872	0.0473
0.4	4.1	11.06	0.0253	0.4852	0.0316
0.5	3.22	7.78	0.0133	0.3072	0.0212

**Table 1:** Corrosion rate (CR) and reaction number (RN) of aluminum in HCl containing various concentrations of Cefuroxime axetil.

C (g/l)	Weight loss		Gasometric		Thermometric
	303K	333K	303K	333K	303K
0.1	66.1	60	73.4	70.14	70.88
0.2	70.52	63.88	77	75.26	75.99
0.3	77.32	69.72	81.12	79.34	79.11
0.4	80.75	73.18	85.25	82.85	83.31
0.5	81.26	77.12	89.87	84.16	86.3

**Table 2:** Inhibition efficiencies of Cefuroxime axetil for the corrosion of aluminum in HCl.

from gravimetric method. However, values of inhibition efficiency obtained from the weight loss were higher than the values obtained from thermometric and gasometric methods indicating that the average inhibition efficiency of CA is better than its instantaneous inhibition efficiency.

The stability of the inhibitive properties of the studied inhibitor over 168 hours of immersion was studied by plotting values of inhibition efficiencies gotten from weight loss studies against time as shown in Figure 2. From the plots, it is also evident that the inhibition efficiency first decreased with time until a critical value was attained after which it started increasing. This trend suggests that at first, there was competition between the forces of adsorption and desorption and that after the critical zone, adsorption facilitated the formation of a protective layer and thus protected the metal against further corrosion attack.

### Effect of temperature


According to Eddy [32], temperature affects the rate of any chemical reaction such that an increase in temperature leads to a corresponding increase in the rate of the reaction. Hence the effect of temperature on the corrosion of aluminum in HCl (in the absence and presence of CA) was studied using the Arrhenius Equation (equation 6) where the apparent activation energies ( $E_a$ ) for the corrosion process in absence and presence of inhibitor were evaluated [6,33].

$$\log \frac{CR_2}{CR_1} = \frac{E_a}{2.303R} \left( \frac{1}{T_1} - \frac{1}{T_2} \right) \quad (6)$$

Where,  $CR_1$  and  $CR_2$  are the corrosion rates of aluminum in solution of HCl at the temperatures,  $T_1$  (303 K) and  $T_2$  (333 K) respectively,  $E_a$  is the activation energy for the adsorption of CA on Al surface and R is the gas constant. Calculated values of the  $E_a$  are shown in Table 3. It can be seen from the table that the activation energies are lower than the value of  $80 \text{ kJmol}^{-1}$  required for a chemical adsorption mechanism supporting the earlier claims the adsorption of CA on aluminum proceeds by physical adsorption mechanism.

### Thermodynamic study

The heat of adsorption ( $Q_{ads}$ ) of Cefuroxime axetil on aluminum surface was calculated using equation (7) [34]

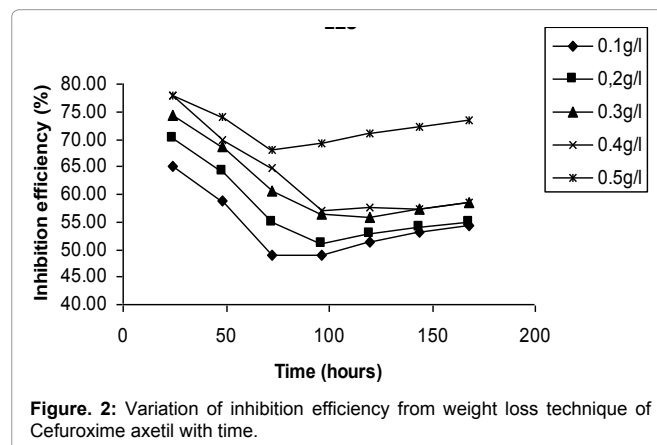

**Figure 2:** Variation of inhibition efficiency from weight loss technique of Cefuroxime axetil with time.



$$Q_{ads} = 2.303R \left( \frac{\theta_2}{1-\theta_2} - \frac{\theta_1}{1-\theta_1} \right) X \left( \frac{T_1 \times T_2}{T_2 - T_1} \right) \quad (7)$$

where  $Q_{ads}$  is the heat of adsorption of CA on Al surface,  $\theta_1$  and  $\theta_2$  are the degrees of surface coverage of the inhibitor at the temperatures,  $T_1$  and  $T_2$  (where  $T_2$  and  $T_1$  are 303 K and 333 K respectively) and R is the gas constant. Values of  $Q_{ads}$  calculated from equation 7 are presented in Table 3. These values are negative indicating that the adsorption of CA on aluminum surface is exothermic.

### Adsorption considerations

Eddy *et al.* [35] stated that adsorption isotherms provide importance clues about the nature of metal inhibitor interaction. The general formula for adsorption isotherm is expressed can be as follows

$$f(0, x) \exp(-2a\theta) = KC \quad (8)$$

where,  $f(0, x)$  is configuration factor,  $\theta$  is the surface coverage, C is inhibitors concentration, K is adsorption constant and a is the molecular interaction parameter.

Data obtained from weight loss, thermometric and gasometric measurements were used to fit curves for different adsorption isotherms, including Temkin, Langmuir, Freundlich, Bockris-Swindles, Flory Huggins and Frumkin isotherm. The test indicated that Langmuir adsorption isotherm best described the adsorption characteristics of CA on the surface of aluminum.

According to Ghasemi and Tizpar [36], if the assumptions of Langmuir adsorption isotherm are valid for the corrosion inhibition reaction, then, it can be assumed that the degree of surface coverage and the concentration of the inhibitor in the bulk electrolyte are related according to the following equation,

$$\frac{\theta}{1-\theta} = b_{ads} C \quad (9)$$

Rearrangement of equation 9, simplifies it to equation (10),

$$\log\left(\frac{C}{\theta}\right) = \log(C) - \log(b_{ads}) \quad (10)$$

From equation 10, plots of  $\log\left(\frac{C}{\theta}\right)$  versus  $\log C$  are expected to yield straight lines with slopes and intercepts equal to unity and  $\log b_{ads}$ . Figure 3 shows the Langmuir isotherm for the adsorption of CA on Al surface. Adsorption parameters deduced from the plots are presented in Table 4. The results obtained reveal that the slopes and  $R^2$  values are very close to unity indicating a strong adherence of the adsorption data to the assumptions establishing the Langmuir model.

C (M)	$E_a$ (KJ/mol)	$Q_{ads}$ (KJ/mol)
Blank	21.7	-
0.1	36.81	-32.43
0.2	41	-35.88
0.3	42.89	-39
0.4	47	-42.1
0.5	49.55	-46.01

**Table 3:** Activation energy and heat of adsorption of Cefuroxime axetil on the surface of aluminum

The equilibrium constant of adsorption (obtained from the Langmuir adsorption isotherm) is related to the equilibrium constant of adsorption according to equation (11) [37]


$$DG_{ads}^0 = -2.303RT \log(55.5K) \quad (11)$$

where K is the equilibrium constant of adsorption, 55.5 is the molar concentration of water,  $G_{ads}$  is the free energy of adsorption of the inhibitor, R is the gas constant and T is the temperature. The free energies calculated from equation 11 are also presented in Table 4. Results presented indicate that the values of  $\Delta G_{ads}^0$  are negative and lies between -10.28 and -11.77 kJ mol<sup>-1</sup>.

According to Bilgic and Sahin [38], values of standard Gibbs free energy of adsorption in aqueous solution around -20 kJ mol<sup>-1</sup> or lower (more positive) indicate adsorption with electrostatic interaction between the adsorbent and adsorbate (physisorption), while those around or higher (more negative) than -40 kJ mol<sup>-1</sup> involve charge sharing between the molecules and the metal (chemisorption). Therefore, the adsorption of CA on aluminum surface is spontaneous and supports the mechanism of physical adsorption.

### Scanning Electron Microscope (SEM)


Figure 4 and 5 show the surface morphology of aluminum exposed to 0.1 M hydrochloric acid in the presence and absence of 0.5 g / L CA respectively. A uniform severe corrosion can be observed in the absence of inhibitor (Figure 4). However, the SEM

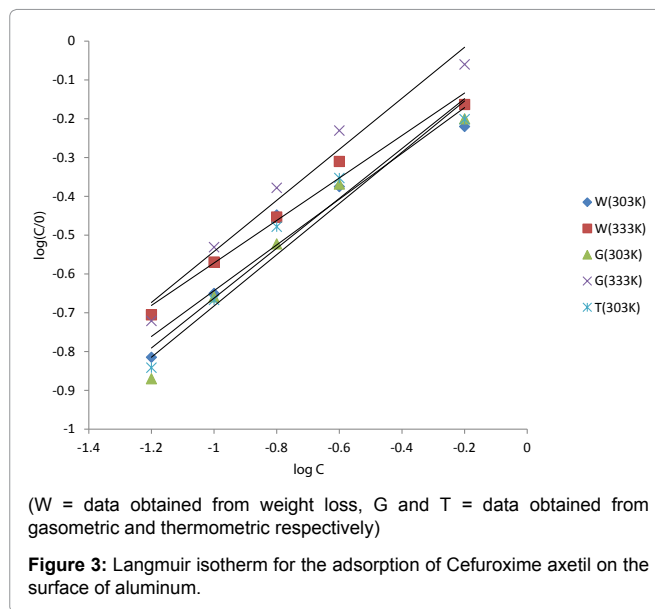

	slope	$\log K_{ads}$	$\Delta G_{ads}^0$ (KJ/ $\mu$ ol)	$R^2$
W (303 K)	0.9744	0.0151	-10.85	0.994
W (303 K)	0.9891	0.0174	-11.77	0.9675
G (303 K)	0.9783	0.0138	-10.28	0.9887
G (333 K)	0.8884	0.0583	-11.46	0.9917
T (303 K)	0.9662	0.0502	-10.56	0.9788

**Table 4:** Langmuir parameters for the adsorption of Cefuroxime axetil on the surface of aluminum.



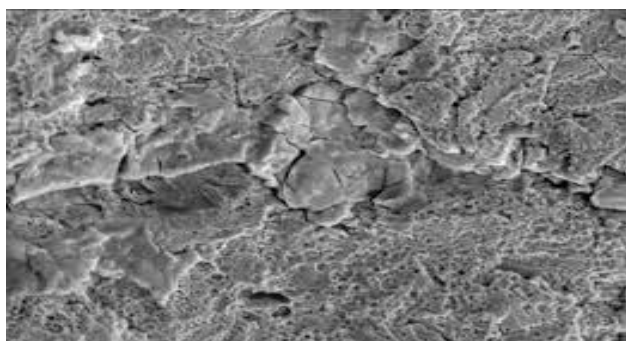

**Figure 4:** SEM of Aluminum exposed to 0.1 M hydrochloric acid in the absence of 0.5 g / L Cefuroxime axetil.



**Figure 5:** SEM of Aluminum exposed to 0.1 M hydrochloric acid in the presence of 0.5 g / L Cefuroxime axetil.

obtained for aluminum in presence of inhibitor (Fig 5) showed that the metal surface is partially covered with inhibitor giving it a reasonable degree of protection which further proves that CA acts as good inhibitor at 0.1 M acid concentration [39].

## Conclusions

From the study, the following conclusions can be drawn. CA efficiently inhibits the corrosion of mild steel in 0.1M HCl medium. Adsorption of CA on the surface of aluminum from 1M HCl obeys Langmuir adsorption isotherm. The inhibition efficiency of CA increases with increasing the inhibitor concentration and on increasing the temperature, the corrosion rate increases. The calculated values of  $E_a$ ,  $Q_{ads}$ ,  $\Delta G_{ads}$  indicates that the adsorption of inhibitor on the metal surface

is physisorption, exothermic and followed by spontaneous process. Protective film formation against the acid attack is confirmed by SEM.

## Acknowledgment

The authors are grateful to TEFUND for sponsoring the research and Mrs Janet Onoja Ameh for typesetting the manuscript.

## References

1. Thompson NG, Yunovich M, Dunmire D. Cost of corrosion and corrosion maintenance strategies (2007) *Corros Rev* 25:247–262.
2. Cherry BW, Skerry BS, Clayton Vic. Corrosion in Australia: the report

- of the Australian National Centre for Corrosion Prevention and Control feasibility Study (1983) Department of Materials Engineering, Monash University:Australia.
3. Patni N, Agarwal S, Shah Pallav. Greener approach towards corrosion inhibition (2013) *Chin J Eng* 2013:1–10.
4. Dalo Abu AM, Othman AA, Rawashdeh AI FAN. Exudate gum from Acacia trees as green corrosion inhibitor for mild steel in acidic media (2012) *Int J Electrochem Sci* 7:9303–9324.
5. Sharma SK, Mudhoo A, Khamis E. Adsorption studies, modeling and use of green inhibitors in corrosion inhibition: an overview of recent research, green corrosion inhibitors: status in developing countries (2011) *Green corrosion chemistry and engineering*. Wiley–VCH Publications:319.
6. Ameh PO, Oyeniyi S, Qand Sani UM. Quantum Chemical Studies on the Corrosion Inhibitions of Mild Steel in Acidic Medium by 5-amino-1-cyclopropyl-7-[(3R,5S)-3,5-dimethylpiperazin-1-yl]-6,8-difluoro-4-oxo-1,4-dihydroquinoline-3-carboxylic acid (2015) *International Journal of Chemical, Material and Environmental Research* 2:1-16.
7. Abdel Hameed RS. Expired drugs as corrosion inhibitors for metals and alloys (2013) *Journal of physical chemistry PCAIJ* 8:146-149.
8. Deepa Rani P, Selvaraj S. Inhibitive action of Vitis vinifera (grape) on copper and brass in natural sea water environment (2010) *Rasayan J Chem* 3:473-482.
9. Saratha R, Kasthuri N, Thilagavathy P. Environment friendly acid corrosion inhibition of mild steel by Ricinus communis Leaves (2009) *Der Pharma Chemica* 1 2:249-257.
10. Satapathy AK, Gunasekaran G, Sahoo SC, Kumar Amit Rodrigues PV. Corrosion inhibition by Justicia gendarussa plant extract in hydrochloric acid solution (2009) *Corros Sci* 51:2848–2856.
11. Morad MS. Inhibition of iron corrosion in acid solutions by Cefatrexyl, Behaviour near and at the corrosion potential (2008) *Corros Sci* 50:436-441.
12. Fouda AS, Al-Sarawy AA, Ahmed FS, El-Abbasy HM. Corrosion inhibition of aluminum 6063 using some pharmaceutical compounds (2009) *Corrosion Science* 51:485–492.
13. Eddy NO, Odoemelam SA. Adsorption and inhibitive properties of norfloxacin for the corrosion of mild steel in  $H_2SO_4$  (2008) *Internat J of Pure and Applied Chem* 3:1-10.
14. Shukla SK, Singh AK, Ahamad I, Quraishi MA. Streptomycin: A commercially available drug as corrosion inhibitor for mild steel in hydrochloric acid solution (2009) *Materials Letters* 63:819.
15. Singh AK, Quraishi MA. Effect of Cefazolin on the corrosion of mild steel in HCl solution (2010) *Corros Sci* 52:152-161.
16. [McEvoy GK. Cephalosporins: cefuroxime sodium and cefuroxime axetil (2003) AHFS Drug Information, American Society of Hospital Pharmacists, Wisconsin Avenue:223-231.
17. Nieves Ruiz-Balaguer, Amparo Nacher, Vicente G. Casabo, and Matilde Merino (1997). Nonlinear Intestinal Absorption Kinetics of Cefuroxime Axetil in Rats. *ANTIMICROBIAL AGENTS AND CHEMOTHERAPY*, Vol. 41, No. 2: 445–448.
18. Ridgway E, Stewart K, Rai G, Kelsey MC, Bielawska C. The pharmacokinetics of cefuroxime axetil in the sick elderly patient (1991) *J Antimicrob Chemother* 27:663-668.
19. Wozniak T, J Hicks. Cefuroxime sodium (1991) *Anal Profiles Drug Subst* 20:209–237.
20. Sommers DK, van Wyk M, Moncrieff J, Schoeman HS. Influence of food and reduced gastric acidity on the bioavailability of bacampicillin and cefuroxime axetil (1984) *Br J Clin Pharmacol* 18:535-539.
21. Finn A, Straughn A, Meyer M, Chubb J. Effect of dose and food on the bioavailability of cefuroxime axetil (1987) *Biopharm Drug Dispos* 8:519-526.
22. McEvoy GK. Cephalosporins: cefuroxime sodium. Cefuroxime axetil (1994) American Society of Hospital Pharmacists Inc:152–159.
23. Williams PE, Harding SM. The absolute bioavailability of oral cefuroxime axetil in male and female volunteers after fasting and after food (1984) *J Antimicrob Chemother* 13:191-196.



24. Foord RD. Cefuroxime: human pharmacokinetics (1976) *Antimicrob Agents Chemother* 9:741-747.
25. Tsuji A, Hirooka H, Tamai I, Terasaki T. Evidence for a Carrier-Mediated Transport System in the Small Intestine Available for FK089, a New Cephalosporin Antibiotic Without an Amino Group (1986) *J Antibiot* 39:1592-1597.
26. Harding SM. Comparative pharmacokinetics of tablets and suspension (1990) *Res Clin Forums* 12:23-29.
27. Bundgaard H. Design of Prodrugs: Bioreversible Derivatives for Various Functional Groups and Chemical Entities (1985) *Design of Prodrugs*, NY Elsevier Science Publishing Co:1-92
28. Oguzie EE. Evaluation of some inhibitive effect of some plant extracts on the acid corrosion of mild steel (2008) *Corros Sci* 50:2993-2998.
29. Nnanna LA, Nwadiuko OC, Ekekwe ND, Ukpabi CF, Udensi SC, et al. Adsorption and Inhibitive Properties of Leaf Extract of *Newbouldia leavis* as a Green Inhibitor for Aluminium Alloy in  $H_2SO_4$  (2011) *American Journal of Materials Science* 1:143-148.
30. Umoren SA, Ebenso EE, Okafor PC, Ogbobe O. Water soluble polymers as corrosion inhibitors of mild steel in acidic medium (2006) *Pigment Resin Technol* 35:346-52.
31. Umoren SA, Ogbobe O, Ebenso EE, Okafor PC. Polyethylene glycol and polyvinyl alcohol as corrosion inhibitors for aluminium in acidic medium (2007) *J Appl Polym Sci* 105:3363-3370.
32. Eddy NO. Inhibition of the corrosion of mild steel in  $H_2SO_4$  by some antibiotics (2008) Ph. D Thesis, University of Calabar.
33. Momoh Yahaya H, Eddy NO, Iyun JF, Gimba CE, Oguzie EE. Inhibitive and Adsorptive Behaviour of Guanine on Corrosion of Mild Steel in 0.1M HCl and  $H_2SO_4$  (2012) *International Journal of Modern Chemistry* 2:127-142.
34. Bhajiwala HM, Vashi RT. Ethanolamine, Diethanolamine and Triethanolamine as Corrosion Inhibitors for Zinc in Binary Acid Mixture [ $HNO_3+H_3PO_4$ ] (2001) *Bull Electrochem Soc* 17:441-448.
35. Eddy NO, Ibok UJ, Ebenso EE. Adsorption, synergistic inhibitive effect and quantum chemical studies on ampicillin and halides for the corrosion of mild steel (2010) *Journal of Applied Electrochemistry* 40:445-456.
36. Ghasemi Z, Tizpar A. The inhibition effect of some amino acids towards Pb-Sb-Se-As alloy corrosion in sulfuric acid solution (2006) *Appl Sci* 252:3667-3672.
37. Flis J, T Zakroczymski. Impedance study of reinforcing steel in simulated pore solution with tannin (1996) *Journal of the Electrochemical Society* 143:2458-2464.
38. Bilgic S, Sahin M. The corrosion inhibition of austenitic chromium-nickel steel in  $H_2SO_4$  by 2-butyn-1-ol (2001) *Mater Chem Phys* 70:290-295.
39. Rafiquee MZA, Khan S, Saxena N, Quraishi MA. Influence of Some Thiadiazole Derivatives on Corrosion Inhibition of Mild Steel in Formic and Acetic Acid Media (2007) *Portugaliae Electrochimica Acta* 25:419-430.